



Standard Specification for Steel, Sheet, Carbon, for Pressure Vessels¹

This standard is issued under the fixed designation A 414/A 414M; the number immediately following the designation indicates the year of original adoption or, in the case of revision, the year of last revision. A number in parentheses indicates the year of last reappraisal. A superscript epsilon (ε) indicates an editorial change since the last revision or reappraisal.

1. Scope*

1.1 This specification² covers hot-rolled carbon steel sheet for pressure vessels involving fusion welding or brazing. Welding and brazing technique is of fundamental importance and shall be in accordance with commercial practices.

1.2 The following grades are included in this specification:

Mechanical Requirements

Grade	Yield Strength, min		Tensile Strength, min	
	ksi	MPa	ksi	MPa
A	25	170	45	310
B	30	205	50	345
C	33	230	55	380
D	35	240	60	415
E	38	260	65	450
F	42	290	70	485
G	45	310	75	515

1.3 Hot-rolled carbon steel sheet is generally furnished in cut lengths and to decimal thickness only. Coils may be furnished, provided tension test specimens are taken to represent the middle of the slab as required by 5.1.4. The purchaser should recognize this requires cutting the coils to obtain test samples and results in half-size coils. The sheet is furnished to the following size limits:

Thickness, in. [mm]	Width, in. [mm]	
	Over 12 to 48 [Over 300 to 1200]	Over 48 [Over 1200]
0.270 to 0.230 [7.0 to 6.0]	sheet (coils only)	sheet (coils only)
Under 0.230 to 0.180 [6.0 to 4.5]	sheet	sheet (coils only)
Under 0.180 to 0.057 [under 4.5 to 1.5]	sheet	sheet

1.4 The values stated in either inch-pound units or SI units are to be regarded separately as standard. Within the text, the SI units are shown in brackets. The values stated in each system are not exact equivalents; therefore, each system shall

be used independently of the other. Combining values from the two systems may result in nonconformance with the specification.

1.5 Tolerances are found in General Requirements Specifications A 568/A 568M and A 635/A 635M. The appropriate General Requirements specification is applied based on the thickness and width of the product ordered.

2. Referenced Documents

2.1 *ASTM Standards:*³

A 568/A 568M Specification for Steel, Sheet, Carbon, and High-Strength, Low-Alloy, Hot-Rolled and Cold-Rolled, General Requirements for

A 635/A 635M Specification for Steel, Sheet and Strip, Heavy-Thickness Coils, Carbon, Hot Rolled

3. Ordering Information

3.1 Orders for material under this specification shall include the following information, as required, to describe the material adequately:

3.1.1 Designation or specification number, date of issue, and grade,

3.1.2 Copper bearing steel, when required,

3.1.3 Special requirements, if required,

3.1.4 Condition—pickled (or blast cleaned), if required. (Material so ordered will be oiled unless ordered dry.), and

3.1.5 Dimensions, including type of edges.

3.1.5.1 As agreed upon between the purchaser and the producer, material ordered to this specification will be supplied to meet the appropriate standard or restricted thickness tolerance table shown in Specification A 568/A 568M.

NOTE 1—Not all producers are capable of meeting all of the limitations of the thickness tolerance tables in Specification A 568/A 568M. The purchaser should contact the producer regarding possible limitations prior to placing an order.

3.1.6 Cast or heat analysis, or test report request, or both, if required.

NOTE 2—A typical ordering description is as follows: “ASTM A 414,

¹ This specification is under the jurisdiction of ASTM Committee A01 on Steel, Stainless Steel, and Related Alloys and is the direct responsibility of Subcommittee A01.19 on Steel Sheet and Strip.

Current edition approved March 1, 2004. Published March 2004. Originally approved in 1971. Last previous edition approved in 2001 as A 414/A 414M – 01.

² For ASME Boiler and Pressure Vessel Code applications see related Specification SA-414 in Section 11 of that Code.

³ For referenced ASTM standards, visit the ASTM website, www.astm.org, or contact ASTM Customer Service at service@astm.org. For *Annual Book of ASTM Standards* volume information, refer to the standard’s Document Summary page on the ASTM website.

*A Summary of Changes section appears at the end of this standard.

Grade A, Hot-Rolled Sheet, 0.100 in. [2.54 mm] by 36 in. [914.4 mm] by 96 in. [2438 mm], cut edges.”

4. Chemical Requirements

4.1 *Cast or Heat Analysis*—The analysis of the steel shall conform to the requirements prescribed in Table 1.

4.1.1 Unspecified elements may be present. Limits on elements shall be as stated in Table 2.

4.1.1.1 Each of the elements listed in Table 2 shall be included in the report of the heat analysis. When the amount of an element present is less than 0.02 %, the analysis may be reported as “<0.02 %.”

4.2 *Product, Check, or Verification Analysis*—Analyses may be made by the purchaser from finished material representing each heat.

4.3 *Deoxidation*—For all grades, killed steel is required. See Table 1 and footnotes A and B.

5. Mechanical Property Requirements

5.1 *Tensile Strength:*

5.1.1 *Requirements*—Material as represented by the test specimen shall conform to the tensile requirements specified in Table 3.

5.1.2 *Number of Tests*—Two tensile tests shall be made from the product of each slab as rolled.

5.1.3 *Location and Orientation* (see Fig. 1):

5.1.3.1 Tensile test specimens shall be taken at locations representing the middle and back end of each slab as rolled.

5.1.3.2 Tensile test samples shall be taken from the full thickness of the sheet as rolled.

5.1.3.3 Tensile test specimens shall be taken from a location approximately halfway between the center of the sheet and the edge of the material as-rolled.

5.1.3.4 Tensile test specimens shall be taken with the axis of the test specimen perpendicular to the rolling direction (transverse test).

5.1.4 *Test Method*—Yield strength shall be determined by either the 0.2 % offset method or by the 0.5 % extension under load method, unless otherwise specified.

6. General Requirements for Delivery

6.1 Material furnished under this specification shall conform to the applicable requirements of the current edition of Specification A 568/A 568M unless otherwise provided herein.

TABLE 2 Limits on Unspecified Elements (See 4.1.1)

Copper, max % ^A	Heat analysis	0.40
	Product analysis	0.43
Nickel, max % ^A	Heat analysis	0.40
	Product analysis	0.43
Chromium, max % ^{A,B}	Heat analysis	0.30
	Product analysis	0.34
Molybdenum, max % ^{A,B}	Heat analysis	0.12
	Product analysis	0.13
Vanadium, max % ^C	Heat analysis	0.03
	Product analysis	0.04
Columbium, max % ^C	Heat analysis	0.02
	Product analysis	0.03

^A The sum of copper, nickel, chromium, and molybdenum shall not exceed 1.00 % on heat analysis. When one or more of these elements are specified, the sum does not apply, in which case, only the individual limits on the remaining unspecified elements will apply.

^B The sum of chromium and molybdenum shall not exceed 0.32 % on heat analysis. When one or more of these elements are specified, the sum does not apply, in which case, only the individual limits on the remaining unspecified elements will apply.

^C By agreement, the heat analysis limits for vanadium or columbium, or both, may be increased up to 0.10 % and 0.05 %, respectively.

7. Workmanship

7.1 The material shall be free from injurious defects (see Specifications A 568/A 568M or A 635/A 635M, as appropriate due to thickness).

8. Finish and Appearance

8.1 *Surface Finish:*

8.1.1 Unless otherwise specified, the material shall be furnished without removing the hot-rolled oxide or scale.

8.1.2 When required, the material may be specified to be pickled or blast cleaned.

8.2 *Oiling:*

8.2.1 Unless otherwise specified, the material shall be furnished not oiled.

8.2.2 When specified to be pickled or blast cleaned, the material shall be furnished oiled. When required, pickled or blast-cleaned material may be specified to be furnished dry.

8.3 *Edges*—Unless otherwise specified, mill edges shall be furnished on material that has not had the hot-rolled oxide or scale removed and cut edges shall be furnished on material that has had the hot-rolled oxide or scale removed.

9. Certification and Reports

9.1 The manufacturer shall furnish copies of a test report showing the results of the heat analysis and mechanical property tests made to determine compliance with this specification. The report shall include the purchase order number,

TABLE 1 Chemical Requirements

Element	Composition — Weight % Heat Analysis						
	Grade A	Grade B	Grade C	Grade D	Grade E	Grade F	Grade G
Carbon, max	0.15	0.22	0.25	0.25	0.27	0.31	0.31
Manganese, max	0.90	0.90	0.90	1.20	1.20	1.20	1.35
Phosphorus, max	0.035	0.035	0.035	0.035	0.035	0.035	0.035
Sulfur, max	0.035	0.035	0.035	0.035	0.035	0.035	0.035
Aluminum	0.02–0.08	0.02–0.08	0.02–0.08	0.02–0.08	0.02–0.08	0.02–0.08	0.02–0.08
Silicon ^{A,B}
Copper, when copper steel is specified, min	0.20	0.20	0.20	0.20	0.20	0.20	0.20

^A Where an ellipsis (. . .) appears in this table, there is no requirement, but the analysis shall be reported.

^B When silicon or aluminum-silicon killed steel is specified, a range of 0.15 to 0.30 shall apply to the silicon and a range of 0.02 to 0.08 shall apply to the aluminum.

TABLE 3 Tensile Requirements

	Grade A	Grade B	Grade C	Grade D	Grade E	Grade F	Grade G
Tensile strength:							
min, ksi [MPa]	45	50	55	60	65	70	75
	[310]	[345]	[380]	[415]	[450]	[485]	[515]
max, ksi [MPa]	60	65	70	75	85	90	95
	[415]	[450]	[485]	[515]	[585]	[620]	[655]
Yield strength, min, ksi [MPa] ^A	25	30	33	35	38	42	45
	[170]	[205]	[230]	[240]	[260]	[290]	[310]
Elongation in 2 in. [50 mm], min, percent:							
Under 0.270 to 0.145 [Under 7.0 to 3.8]	26	24	22	20	18	16	16
Under 0.145 to 0.089 [Under 3.8 to 2.2]	24	22	20	18	16	14	14
Under 0.089 to 0.057 [Under 2.2 to 1.5]	23	21	19	17	15	13	13
Elongation in 8 in. [200 mm], min, percent:							
Under 0.270 to 0.145 [Under 7.0 to 3.8]	20	18	16	14	12	10	10

^A Yield strength determined by the 0.2 % offset or 0.5 % extension under load methods.

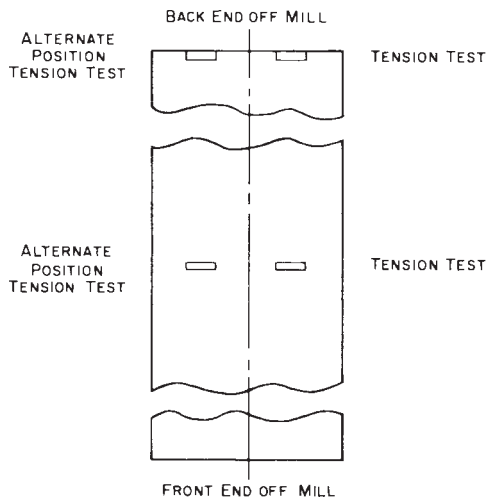


FIG. 1 Location of Test Specimens

10. Product Marking

10.1 The name or brand of the manufacturer, heat and slab number, specification designation number, and grade shall be legibly and durably marked on each cut length sheet in two places not less than 12 in. [300 mm] from the edges. Cut length sheets, the maximum lengthwise and crosswise, dimensions of which do not exceed 72 in. [1800 mm], shall be legibly and durably marked in one place approximately midway between the center and a side edge. The manufacturer's test identification number shall be legibly and durably marked on each test specimen. Steel-die marking of sheets is prohibited.

10.2 For coil product, the information required in 10.1 shall be legibly and durably marked both on each coil and on a tag affixed to each coil.

11. Keywords

11.1 carbon steel sheet; pressure vessel steels; steel sheet

specification number, and test identification number correlating the test results with material represented.

SUMMARY OF CHANGES

Committee A01 has identified the location of selected changes to this standard since the last issue, A 414/A 414M-01, that may impact the use of this standard. (Approved March 1, 2004.)

- (1) Deleted Footnote A in Section 1.3. emphasize the use of the appropriate standard based on the
- (2) Added new Section 1.5 to replace Footnote A and to ordered material size.

ASTM International takes no position respecting the validity of any patent rights asserted in connection with any item mentioned in this standard. Users of this standard are expressly advised that determination of the validity of any such patent rights, and the risk of infringement of such rights, are entirely their own responsibility.

This standard is subject to revision at any time by the responsible technical committee and must be reviewed every five years and if not revised, either reapproved or withdrawn. Your comments are invited either for revision of this standard or for additional standards and should be addressed to ASTM International Headquarters. Your comments will receive careful consideration at a meeting of the responsible technical committee, which you may attend. If you feel that your comments have not received a fair hearing you should make your views known to the ASTM Committee on Standards, at the address shown below.

This standard is copyrighted by ASTM International, 100 Barr Harbor Drive, PO Box C700, West Conshohocken, PA 19428-2959, United States. Individual reprints (single or multiple copies) of this standard may be obtained by contacting ASTM at the above address or at 610-832-9585 (phone), 610-832-9555 (fax), or service@astm.org (e-mail); or through the ASTM website (www.astm.org).